

# Hexoloy® SG Silicon Carbide

## Saint-Gobain Advanced Ceramics Structural Ceramics

Hexoloy® SG Silicon Carbide is a unique electrically conductive analog of sintered silicon carbide.


### Technical Specifications

Property	Units	Measurement Technique	Value
Phases	–	X-ray Diffraction	SiC (6H, 4H, 15R), C
Density	gm/cm <sup>3</sup>	–	3.0
Hardness	kg/mm <sup>2</sup>	Knoop, 100 gm load	2800
Flexural Strength Room Temperature	MPa	ASTM C-1161, 4-point	311
Weibull Modulus	–	ASTM C-1161, 4-point	18
Young's Modulus	GPa	Pulse Echo	376
Shear Modulus	GPa	Pulse Echo	161
Poisson's Ratio	–	Pulse Echo	0.17
Fracture Toughness (Room Temperature)	MPa.m <sup>1/2</sup>	Indentation, 10 kg load	3.9
Coefficient of Thermal Expansion (RT-700°C)	10 <sup>-6</sup> mm/mm K	Dilatometry	4.6
Mean Specific Heat @ RT	J/g K	Laser Flash ASTM E 1461-92	0.65
Thermal Conductivity @ RT	W/m K	Laser Flash ASTM E 1461-92	118
Thermal Conductivity @ 200°	W/m K	Laser Flash ASTM E 1461-92	92
Thermal Conductivity @ 400°	W/m K	Laser Flash ASTM E 1461-92	70
Electrical Resistivity	Ohm-cm	–	1.0 - 10.0
Free Carbon	%	Combustion	5.35
Total Carbon	%	Combustion	34.6

The information, recommendations, and opinions set forth herein are offered solely for your consideration, inquiry and verification and are not, in part or total, to be construed as constituting a warranty or representation for which we assume legal responsibility. Nothing contained herein is to be interpreted as authorization to practice a patented invention without a license.

Hexoloy® is a trademark of Saint-Gobain Advanced Ceramics Corporation

### Hexoloy® SG SiC – 200X

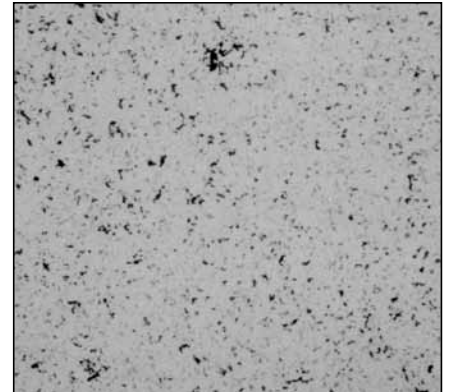

Hexoloy® SG SiC offers a wide variety of desirable properties in one package including:

- Excellent Hardness
- Corrosion resistance
- High temperature stability

Saint-Gobain Ceramics  
Structural Ceramics  
Hexoloy® Products  
23 Acheson Drive  
Niagara Falls, New York 14303  
Telephone: 716-278-6233  
Fax: 716-278-2373  
E-mail: [scd.sales@saint-gobain.com](mailto:scd.sales@saint-gobain.com)  
[www.hexoloy.com](http://www.hexoloy.com)

©2012 Saint-Gobain Ceramics  
All Rights Reserved  
Form No. B-1000  
5/12 QTY. 500