

Hexoloy® SP Silicon Carbide



Technical Data

Product Description


Hexoloy® SP SiC is a sintered alpha silicon carbide material designed specifically for optimum performance in sliding contact applications such as mechanical seal faces and product lubricated bearings. This material improves upon the exceptional friction properties of Hexoloy® SA SiC (sintered alpha SiC) through the addition of spherical pores. These pores are discrete, non-interconnecting and dispersed in a controlled manner throughout the body of the material. The spherical pores act as fluid or lubricant reservoirs helping to promote the retention of a fluid film at the interface of sliding component surfaces. This “pore” based lubrication mechanism allows Hexoloy® SP SiC to outperform conventional reaction-bonded and sintered silicon carbides in a wide variety of service conditions.

Performance Testing

Corrosion Resistance. Unlike reaction-bonded silicon carbides and tungsten carbides, Hexoloy® SP SiC contains no free silicon phase or metallic binder subject to corrosive attack. This material is a fine grain, single phase SiC product produced via pressureless sintering of submicron silicon carbide powder. As a result of this homogenous SiC composition, it exhibits the same outstanding corrosion resistance as does its forerunner Hexoloy® SA SiC. Superior performance is assured across a nearly universal range of environments including both strong acids and bases. Hexoloy® SP SiC’s corrosion resistance exceeds that of all reaction-bonded SiC’s, tungsten carbides and aluminum oxides.

Corrosion Test Results in Liquids

Test Environment*		Corrosive Weight Loss (mg/cm ² yr)**			
Conc. Reagent (Wt%)	Temp. (°C)	Hexoloy® SP (No Free Si)	Reaction Bonded SiC (12% Si)	Tungsten Carbide (6% Co)	Aluminum Oxide (99%)
98% H ₂ SO ₄	100	1.8	55.0	>1000	65.0
50% NaOH	100	2.5	>1000	5.0	75.0
53% HF	25	<0.2	7.9	8.0	20.0
85% H ₃ PO ₄	100	<0.2	8.8	55.0	>1000
70% HNO ₃	100	<0.2	0.5	>1000	7.0
45% KOH	100	<0.2	>1000	3.0	60.0
25% HCl	70	<0.2	0.9	85.0	72.0
10% HF plus 57% HNO ₃	25	<0.2	>1000	>1000	16.0

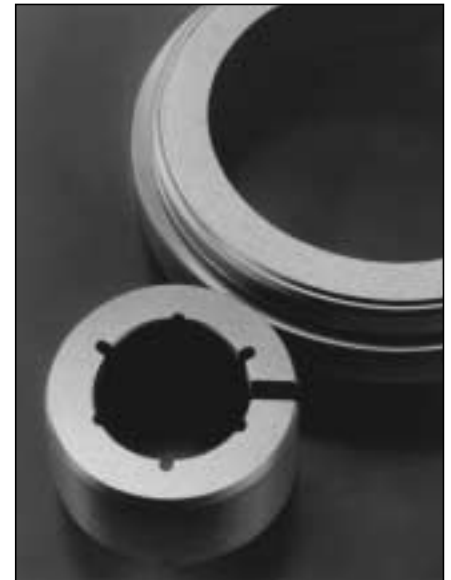

***Test Time:** 125 to 300 hours of submersive testing, continuously stirred.

****Corrosion Weight Loss Guide:**


>1000 mg/cm ² yr	Completely destroyed within days.
100 to 999 mg/cm ² yr	Not recommended for service greater than a month
50 to 100 mg/cm ² yr	Not recommended for service greater than one year
10 to 49 mg/cm ² yr	Caution recommended, based on the specific application.
0.3 to 9.9 mg/cm ² yr	Recommended for long term service
<2 mg/cm ² yr	Recommended for long term service; no corrosion, other than as a result of surface cleaning, was evidenced.

Performance Testing

Seal Face Testing. Seal face performance tests comparing Hexoloy® SP SiC with conventional fine grained reaction-bonded SiC and sintered SiC were conducted on a high pressure test rig. All of the SiC materials were tested running against identical phenolic resin impregnated carbon-graphites. Maximum tested PV (pressure-velocity) exceeded 1 million psi ft/min. Hexoloy® SP demonstrated consistently superior results compared to reaction-bonded and sintered SiC in terms of both carbon-graphite and silicon carbide wear. Additionally, self-mated testing of this material shows excellent service potential for those applications which can benefit from a hardface versus hardface mechanical face seal combination.


Test Conditions

Item	Value(s)
Hydraulic Pressure (Test Pressures)	10, 25, 50, 75, 125 bar 147, 367, 735, 1102, 1837 PSI
Speed	3000 RPM, 9.4 m/s 3000 RPM, 31 ft/s
PV	55-364 bar m/s 157,000-1,250,000 psi ft/min
Temperature	60°C 140°F
Duration	48 hours (per pressure step)
Seal Diameter	75mm (O.D.) 2.953 In. (O.D.)
Wear Track Diameter	59.5mm 2.343 in.

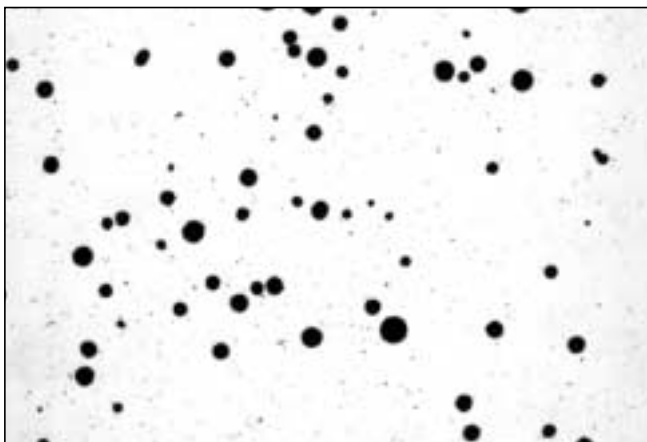


This photomicrograph shows the typical appearance of pores at a magnification of 50X.


Power Consumption

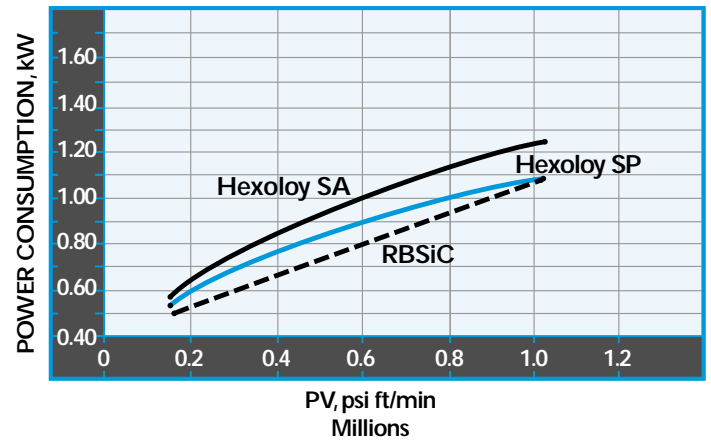

Wear Rate: SiC

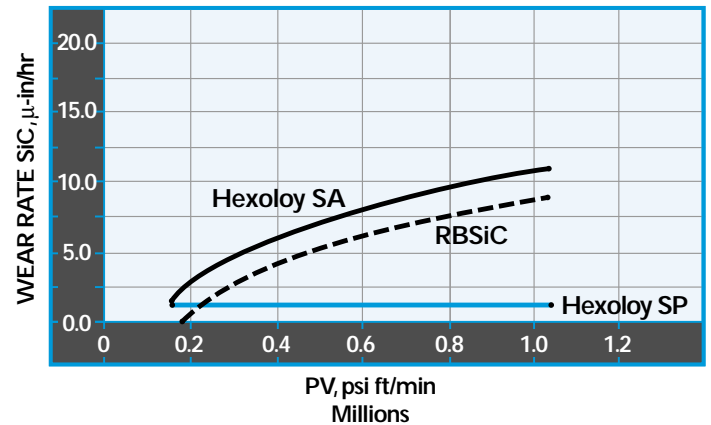

Wear Rate: Carbon

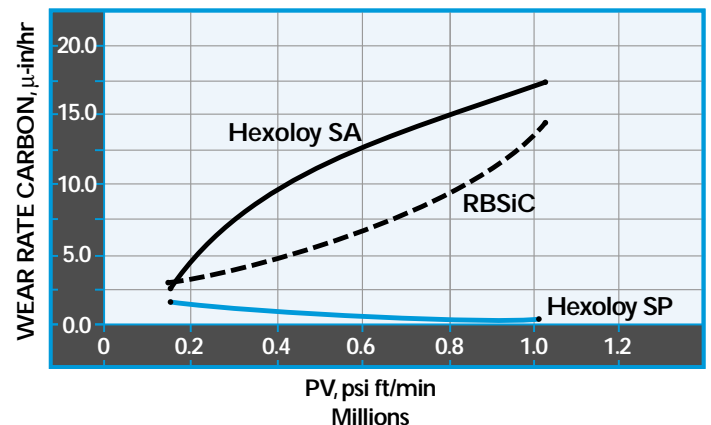

Applications

Industrial Seal Faces

Hexoloy® SP SiC offers mechanical seal manufacturers and users a material they can broadly standardize on without sacrifice. Universal corrosion resistance combined with excellent tribological characteristics makes Hexoloy® SP SiC the superior choice for a wide range of industrial seal face applications:

- Chemical processing
- Waste water
- Mining
- Marine
- Refining
- Paper and pulp
- Nuclear
- Appliance

Automotive Water Pump Seal Faces

In highly silicated coolants Hexoloy® SP SiC has demonstrated improvement in service life over the excellent performance of Hexoloy® SA for both automotive and truck application. Hexoloy SP is used commercially in automotive SiC versus hard carbon seal designs, and has shown superior results in SiC versus SiC hard-face designs for diesel truck applications.

Pump Bearings

Seal-less pumps equipped with Hexoloy® SP SiC sleeve and thrust bearings have been able to run dry during process upset conditions up to twice as long as have pumps equipped with conventional sintered and reaction-bonded SiC's. Hexoloy® SP SiC is the one bearing material available today which can handle the full spectrum of application demands from suspended abrasives to hydrofluoric acids to light-hydrocarbons.

Relative Ranking of Commonly Used Seal Face Materials

Key Material Attributes	Hexoloy SP SiC	Sintered SiC	Reaction-Bonded SiC	Tungsten Carbide	Aluminum Oxide
1. Running Capability Versus Carbon-Graphite	Superior	Excellent	Excellent	Good	Fair
2. Running Capability Versus Itself	Superior	Fair-Good	Fair-Good	Poor	Poor
3. Universal Corrosion Resistance	Superior	Superior	Fair	Fair	Fair
4. Good Thermal Management	Superior	Excellent	Excellent	Fair-Good	Poor
5. Abrasive Wear Resistance (Slurry Applications)	Superior	Superior	Good	Good	Fair
6. Economics (Hi-Volume Moldable)	Excellent	Excellent	Fair	Fair	Excellent



Typical sealface and bearing components currently fabricated in Hexoloy® SP SiC.

Hexoloy® SP SiC Typical Physical Properties

Property	Units	Typical Value
Composition*	–	SiC
Grain Size	µm	4-10
Density	g/cm ³	3.04
Hardness (Knoop)**	kg/mm ²	2800
Flexural Strength 4 pt @ RT***	MPa x10 ³ lb/in ²	240 35
Modulus of Elasticity @ RT	GPa x10 ⁶ lb/in ²	400 58
Weibull Modulus (2 parameter)		19
Poisson Ratio		0.14
Fracture Toughness @ RT Double Torsion & SENB	MPa x m ^{1/2} x10 ³ lb/in ² x in ^{1/2}	4.3 3.9
Coefficient of Thermal Expansion RT to 700°C	x10 ⁻⁶ mm/mmK x10 ⁻⁶ in/in °F	4.2 2.3
Mean Specific Heat @ RT	J/gmK	0.59
Thermal Conductivity @ RT	W/mK Btu/ft h °F	110 64
Pore Volume Fraction	%	4.0-6.0
Pore Size (Typical)	µm	50

*Composition code: Si = free silicon metal;
C = free graphite; SiC = silicon carbide

***Test Bar Size: 3 x 4 x 45 mm
(0.118" x 0.157" x 1.772")

**Knoop 0.1 kg load

Design Considerations

Successful application of engineered ceramic materials such as Hexoloy® SP SiC is heavily dependent on proper design criteria. Among the many aspects of product design requiring careful consideration are:

- Physical Properties
- Tribological Performance
- Process Capability/Economics
- Attachment or Drive Method
- Geometric Shape
- Effect of Tolerances on Cost
- Surface Finish Requirements

Saint-Gobain Ceramics application engineers can assist you with the design of cost-effective high performance components for your specific need.

The information, recommendations and opinions set forth herein are offered solely for your consideration, inquiry, and verification and are not, in part or total, to be construed as constituting a warranty or representation for which we assume legal responsibility. Nothing contained herein is to be interpreted as authorization to practice a patented invention without a license.

Hexoloy® is a registered trademark of Saint-Gobain Ceramics.

North America

Saint-Gobain Ceramics
Structural Ceramics
Hexoloy® Products
23 Acheson Drive
Niagara Falls, New York 14303
Telephone: 716-278-6233
Fax: 716-278-2373
E-mail: scd.sales@saint-gobain.com
www.hexoloy.com

Europe

Saint-Gobain Advanced Ceramics GmbH
Postfach 401254 • Nobelstrasse 6
41189 Monchengladbach, Germany
Phone: 49-21665-509-0
Fax: 49-21665-509-10

©2003 Saint-Gobain Ceramics
All Rights Reserved
Form No. B-1002
10/03 supercedes 2/03